

Thermally activated reorientation of di-interstitial defects in silicon

Jeongnim Kim,¹ Florian Kirchhoff,² Wilfried G. Aulbur,¹ John W. Wilkins,¹

Furrukh S. Khan,² and Georg Kresse³

¹ *Department of Physics, Ohio State University, 43210*

² *Department of Electrical Engineering, Ohio State University, 43210*

³ *Institut für Theoretische Physik, Technische Universität Wien, Wiedner Hauptstraße 8-10/136,
A-1040 Wien, Austria*

Abstract

We propose a di-interstitial model for the P6 center commonly observed in ion implanted silicon. The di-interstitial structure and transition paths between different defect orientations can explain the thermally activated transition of the P6 center from low-temperature C_{1h} to room-temperature D_{2d} symmetry. The activation energy for the defect reorientation determined by *ab initio* calculations is 0.5 eV in agreement with the experiment. Our di-interstitial model establishes a link between point defects and extended defects, di-interstitials providing the nuclei for the growth.

PACS numbers: 61.72.-y, 61.72.Cc, 61.72.Ji, 71.55.-i

Transient enhanced diffusion (TED) in boron-implanted silicon is the limiting factor in controlling dopant profiles for submicron Si-based devices. Interstitial defects in bulk Si generated during implantation have been identified as the sources for boron TED [1–3]. A class of macroscopical interstitial defects, namely $\{311\}$ defects, was suggested to emit interstitials that can contribute to the enhancement of boron diffusion under typical implantation conditions [1,2]. Decreasing the ion implantation energy can suppress the formation of macroscopic $\{311\}$ defects, thus reducing boron TED. However, boron TED exists even at very low implantation energy (below 10 keV) in samples with no visible $\{311\}$ defects [3]. This implies that microscopic interstitial defects, e.g., interstitial clusters, contribute to boron TED.

The activation energy of boron TED, a measure of the energy required to dissociate interstitials from the interstitial complexes, is lower in samples without visible $\{311\}$ defects. Interstitial clusters can become important sources for boron TED at low temperature at which the extended $\{311\}$ defects are still stable against dissociation. Several defect states have been associated with interstitial clusters [4–6]. One of them is the P6 center commonly observed by electron paramagnetic resonance (EPR) measurements in low-energy ion-implanted, proton- or neutron-irradiated silicon [4,5]. The P6 center has $\{100\}$ symmetry, distinct from the typical $\{110\}$ symmetry of vacancy-related defects. At low temperature (200 K), the symmetry of the P6 center is either C_2 or C_{1h} with a twofold axis parallel to the $\langle 100 \rangle$ direction. A thermally-activated symmetry transition occurs at room temperature (300 K) and the symmetry of the P6 center becomes D_{2d} [7]. Motional averaging effects have been suggested to cause the transition [4,5]. Complementary measurements of the ^{29}Si hyperfine structure and the stress alignment indicate that the P6 center arises from *di-interstitial* defects. The stable di-interstitial is an important “precursor” of interstitial clusters and more extended defects such as $\{311\}$ defects. Yet, the structure and dynamics of the di-interstitial have not been fully understood at an atomic scale and no first-principle calculations are available to our knowledge.

In this letter, we propose a microscopic structure of a *di-interstitial* whose low-

temperature symmetry properties and electronic structure are consistent with the P6 center. Furthermore, the structure and transition paths between different defect orientations (Fig. 1) can account for the experimental symmetry transition to D_{2d} at room temperature [4,5]. The activation energy of the defect reorientation in our model is 0.5 eV in excellent agreement with 0.6 eV, the experimental activation energy extracted from the response of the P6 center to an external uniaxial stress [5]. The experimental characterization of the donor level is also consistent with the calculated defect gap states.

The atomic and electronic structure of di-interstitial defects are determined by *ab initio* total energy calculations within the local density approximation (LDA) and generalized gradient approximation (GGA) [8,9]. The local minimum and metastable structures are obtained by structural minimizations using the conjugate gradient method. Starting geometries are stable configurations obtained by molecular dynamics simulations and structural relaxations using tight-binding Hamiltonians [10–12]. In the *ab initio* calculations, the structural minimizations employ two supercell sizes: (i) supercell A consisting of 120 atoms and (ii) supercell B consisting of 72 atoms. The total energy and structure are well converged with the plane-wave energy cutoff of 140 eV and 4 k -points in supercell A [13].

Figure 1(a) shows our di-interstitial model of C_{1h} symmetry, with the twofold axis parallel to the z axis [7]. The basic constituents of the model are a center atom I_0 and dumbbell atoms I_1 - I_2 . Lee recently proposed a di-interstitial model composed of the same building blocks [5,14]. Our model differs from Lee’s model in (i) the orientation of the dumbbell atoms and (ii) the location of the center atom. The dumbbell structure, aligned parallel to the $[110]$ direction, resembles the $\langle 110 \rangle$ interstitialcy, the most stable point defect [15]. Our suggestion that the di-interstitial can be formed when an interstitial is captured by the $\langle 110 \rangle$ interstitialcy is supported by the positive binding energy of the C_{1h} di-interstitial with respect to isolated interstitials (Table I).

Four equivalent C_{1h} di-interstitial configurations, distinguished by the location of the center atom, can be constructed with three interstitials sharing one regular lattice site denoted as o in Fig. 2(a). The *low temperature* symmetry containing a twofold symmetry axis

parallel to $\langle 100 \rangle$ is consistent with the C_{1h} symmetry of our model [4,5]. Figure 2(b) illustrates the four equivalent sites under D_{2d} symmetry which the center atom can occupy [7]. Thermal averaging motions among four C_{1h} configurations with a small activation energy barrier can result in the *room temperature* D_{2d} symmetry.

Indeed, we can identify transition paths that lead to the thermal averaging motion between four local minima. Three transitions – denoted as T_i , $i = x, y, z$, according to the twofold symmetry axis of its saddle point – have the same energy barrier of 0.5 eV.

T_z transition: The transition from the center atomic site I_0 to its mirror image $\otimes$, *cf.* Fig. 1(a), with respect to the $\{\bar{1}10\}$ plane can occur by a displacement of the atom I_0 along the $[110]$ direction. The saddle point of the T_z transition has C_{2v} symmetry with a symmetry axis along z . The orientation of the dumbbell atoms remains the same after the T_z transition.

T_x transition (Fig. 1(b)): A displacement of I_1 along the $[101]$ direction results in a I_0 - I_1 dumbbell pair and the atom I_2 becomes the center atom denoted as I_0^* . The symmetry axis of the saddle point (C_{2v} in Fig. 1(b)) is parallel to the $[100]$ direction. The T_y transition is similar to the T_x transition, I_2 moving along the $[011]$ direction. As the result of the T_x and T_y transitions, the orientation of the dumbbell atoms changes from the $[110]$ direction to the $[\bar{1}10]$ direction.

The *room temperature* D_{2d} symmetry can be explained by the thermal averaging motion of three interstitials I_0, I_1 and I_2 alternatively occupying the four center atomic sites (Fig. 2(b)). Note that the T_i transitions leading to the thermal motional averaging of the D_{2d} symmetry involve a displacement of only one of three interstitials along a C_{2v} saddle point at each transition. The schematics of the potential surface along the high symmetry path is presented in Fig. 3. No other local minima are found along the path $C_{1h} - C_{2v} - C_{1h}$. The experimental D_{2d} symmetry is very plausible within our model, since the low transition energy barrier of 0.5 eV permits frequent T_x, T_y and T_z transitions to motionally average the four C_{1h} configurations accessible to three interstitials.

Structure and energetics of di-interstitial. Table I shows the formation energies E_f and binding energies E_b of the C_{1h} di-interstitial, the metastable C_{2v} di-interstitial and the $\langle 110 \rangle$ interstitialcy. Our LDA formation energy of the $\langle 110 \rangle$ interstitialcy agrees with that obtained by a previous LDA calculation [15]. In general, the bond lengths involved with the defect core atoms I_0, I_1 and I_2 are slightly longer than the bulk bond length of 2.35 Å. Charge density analyses confirm that the defect bonds are indeed weaker than the ideal bulk bonds. The strongest bond for both C_{1h} and C_{2v} di-interstitials is formed between the dumbbell atoms I_1 and I_2 .

Supercell B composed of 72 atoms is not large enough to quantitatively describe the energetics and structural properties of the C_{1h} and C_{2v} di-interstitials. We find a reduction in the transition energy barrier Δ from 0.6 (supercell B) to 0.5 eV (supercell A) due to the relaxation of the third- and fourth-neighbor-shell atoms from the defect core. The bond lengths associated with the defect core can differ by as much as 0.3 Å between supercells A and B. The structural properties of supercell B are *qualitatively different* from those obtained by supercell A [16]. However, supercell A is sufficiently large for the converged energetics and structural properties [13,17].

We find large discrepancies between LDA and GGA in the formation E_f and binding energies E_b , obtained by supercell calculations with *different number of atoms*. This is attributed to the larger bulk cohesive energy of GGA compared to LDA. On the other hand, the relative stability of the C_{1h} and C_{2v} di-interstitials indicated by Δ and structural properties are insensitive to the choice of the exchange-correlation potential V_{xc} . The formation energy differences between supercells A and B are of the order of 0.1 eV within LDA. Similar differences are obtained with GGA. The dynamical process for the symmetry transition schematically shown in Fig. 3 is not influenced by V_{xc} . Typical differences between LDA and GGA results are less than 0.005 Å in bond lengths and less than 0.5° in bond angles for the same supercell size.

Electronic structure of di-interstitial. The experimental analysis of the EPR signal of the positively charged P6 center indicates that the donor level is strongly localized on the center

atom [5]. Figure 4 shows that the defect gap states of the C_{1h} di-interstitial are strongly localized. The donor level has strong p -character mostly localized on the atom I_0 , while the acceptor level is mainly localized on the dumbbell atoms I_1 - I_2 . The donor level of the C_{1h} di-interstitial is located at $E_v + 0.1$ eV and the acceptor level at $E_c - 0.2$ eV.

For the metastable C_{2v} di-interstitial, the donor and acceptor levels become almost degenerate and form a deep level at $E_v + 0.4$ eV. The metastable C_{2v} di-interstitial becomes a stable defect when it is positively charged. The dashed line in Fig. 3 presents a schematic potential surface along the high symmetry path. Self-consistent calculations give a smaller energy difference of 0.14 eV between C_{1h}^{++} and C_{2v}^{++} configurations. Our calculations on neutral and doubly-charged di-interstitials further support the effective D_{2d} symmetry of the P6 center even at room temperature.

Link to extended defects. The stable di-interstitial is the link between point defects and extended defects. The dumbbell atoms of the di-interstitial are reminiscent of the $\langle 110 \rangle$ interstitialcy, suggesting the di-interstitial is formed by an existing $\langle 110 \rangle$ interstitialcy capturing an interstitial. Previously, we found a stability hierarchy of interstitial defects from molecular dynamics simulations with a tight-binding Hamiltonian [10]: the formation energy decreases in the order of interstitial clusters $\rightarrow$ interstitial chains $\rightarrow$ $\{311\}$ defects. A strong tendency of clustering of interstitials has been also predicted from classical molecular dynamics simulations [18]. When the interstitials are saturated such as in ion-implanted samples, the di-interstitials can play the role of nuclei for the extended interstitial defects, initially by providing interstitial sinks to form elongated interstitial clusters and eventually interstitial chains. We note that di-interstitials, larger interstitial clusters, and interstitial chains are composed of a common building block, the $\langle 110 \rangle$ interstitialcy [10]. The aggregation of interstitial chains, in turn, can lead to the formation of extended $\{311\}$ defects.

In conclusion, we present first-principle calculations for structural and electronic properties of di-interstitial defects and relate our stable di-interstitial structure to the P6 center. The C_{1h} di-interstitial model and the transition paths involving the metastable C_{2v} di-interstitial can account for different symmetries of the P6 center both at low and room

temperature. The activation energy of the defect reorientation is 0.5 eV in excellent agreement with experiments. The localization of the donor level also agrees with the experimental characterization.

We wish to thank Dr. Y. H. Lee for useful discussions. This work is supported by NSF and computational aids are provided by OSC, NCSA and NPACI. FK acknowledges support by the NRL component of the DoD CHHSI program. The calculations have been performed using the ab-initio total-energy and molecular-dynamics program VASP (Vienna ab-initio simulation program) developed at the Institut für Theoretische Physik of the Technische Universität Wien.

REFERENCES

- [1] D. J. Eaglesham, P. A. Stolk, H.-J. Gossmann, and J. M. Poate, Appl. Phys. Lett. **65**, 2305 (1994).
- [2] P. A. Stolk, H.-J. Gossmann, D. J. Eaglesham, and J. M. Poate, Appl. Phys. Lett. **66**, 568 (1995).
- [3] L. H. Zhang, K. S. Jones, P. H. Chi, and D. S. Simons, Appl. Phys. Lett. **67**, 2025 (1995).
- [4] Y. H. Lee, N. N. Gerasimenko, and J. W. Corbett, Phys. Rev. B **14**, 4506 (1976).
- [5] Y. H. Lee, Appl. Phys. Lett. **73**, 1119 (1998).
- [6] J. L. Benton, S. Libertino, P. Kringhoj, D. J. Eaglesham, J. M. Poate, and S. Coffa, J. Appl. Phys. **82**, 120 (1997).
- [7] The twofold axis of the C_{1h} and D_{2d} symmetry is chosen to be parallel to $z = [001]$. The D_{2d} group contains two additional twofold axes (x and y) and $\{110\}$ and $\{\bar{1}10\}$ reflection planes.
- [8] W. Kohn and L. J. Sham, Phys. Rev. **140** A1133 (1965).
- [9] G. Kresse and J. Hafner, Phys. Rev. B **47**, 558 (1993); *ibid.* **49**, 14 251 (1994); G. Kresse and J. Furthmüller, Comput. Mat. Sci. **6**, 15 (1996); G. Kresse and J. Furthmüller, Phys. Rev. B **55**, 11 169 (1996) and references therein.
- [10] J. Kim, J. W. Wilkins, F. S. Khan, and A. Canning, Phys. Rev. B **55**, 16186 (1997).
- [11] I. Kwon, R. Biswas, C. Z. Wang, K. M. Ho, and C. M. Soukoulis, Phys. Rev. B **49** 7242 (1994).
- [12] T. Lenosky, J. D. Kress, I. Kwon, A. F. Voter, B. Edwards, D. F. Richards, S. Yang and J. B. Adams, Phys. Rev. B **55** 1528 (1997).

- [13] We checked the convergence by increasing the number of k-points to 32 and the plane wave energy cutoff to 200 eV for the 72-atom supercell. The formation energy of the $\langle 110 \rangle$ interstitialcy changes by 60 meV and the relaxed structure is indistinguishable from calculations using 4 k-points and 140 eV. The energy difference between the C_{1h} and C_{2v} di-interstitials is converged within few meV. The structural properties and relative energetics are well converged for supercell A calculations, confirmed by the less than 10 meV difference in the formation energies between 300- and 120-atom supercell calculations using a TB Hamiltonian of Ref. [12].
- [14] We find the di-interstitial model proposed by Lee [5] is unstable. The local minimum structure obtained by the conjugate gradient minimization under C_2 symmetry constraints has a binding energy of 0.1 eV, much smaller than 1.8 eV of the C_{1h} di-interstitial.
- [15] J. Zhu, T. D. de la Rubia, L. Y. Yang, C. Mailhoit, and G. H. Gilmer, Phys. Rev. B **54**, 4741 (1996) and references therein.
- [16] The dumbbell atoms in supercell B are pushed toward the atoms b and b^* making long bonds ($\sim 2.6\text{\AA}$) with the next-nearest-neighbor shell atoms.
- [17] We find that the tight-binding Hamiltonian by Lenosky *et al.* [12] describes the structures and relative energetics of the di-interstitials and the $\langle 110 \rangle$ interstitialcy quantitatively well compared to *ab initio* calculations.
- [18] G. H. Gilmer, T. D. de la Rubia, D. M. Stock, and M. Jaraiz, Nucl. Instrum. Methods B **102**, 247 (1995).

TABLES

TABLE I. Di-interstitial (DI) formation energies E_f and binding energies E_b . The binding energy is defined as $E_b = -(E_f - 2E_f(I))$, where $E_f(I)$ is the formation energy of an isolated $\langle 110 \rangle$ Interstitialcy. Supercell A consists of 120 bulk atoms, while supercell B consists of 72 bulk atoms. The orientation of the super cells is $[110] \times [\bar{1}10] \times [001]$. The energy barrier Δ is the total energy difference between C_{1h} and C_{2v} di-interstitials for the same supercell.

		Supercell A		Supercell B	
		LDA	GGA	LDA	GGA
C_{1h} DI	E_f	4.93	6.01	4.92	6.03
	E_b	1.78	1.86	2.02	2.10
C_{2v} DI	E_f	5.40	6.51	5.48	6.60
	E_b	1.30	1.36	1.46	1.53
Δ		0.47	0.50	0.55	0.57
$\langle 110 \rangle$ I	$E_f(I)$	3.35	3.93	3.47	4.07


FIGURES

FIG. 1. (a) Atomic structure of a C_{1h} di-interstitial projected on the $\{\bar{1}10\}$ and $\{110\}$ planes and (b) atomic structures of the di-interstitial core during a transition between two C_{1h} configurations. A regular lattice site located at the origin of the axes is shared by three atoms – (i) the center atom I_0 and (ii) the $\langle 110 \rangle$ dumbbell atoms I_1 - I_2 . The site $\otimes$ is related to the site I_0 via a mirror reflection across the $\{\bar{1}10\}$ plane. Three transition paths T_x, T_y and T_z with the same energy barrier of 0.5 eV are identified. The C_{2v} symmetry of the saddle point has a twofold axis parallel to the subscript of the transition $T_i, i = x, y, z$. For example, the transition T_x in (b) displaces the center atom I_0 to I_0^* site and the twofold axis of the saddle point in the middle is parallel to the $[100]$ direction.


FIG. 2. (a) Atomic structure of a C_{1h} interstitial and (b) schematics representing the four equivalent sites of the center atom I_0 under D_{2d} symmetry operations. The regular site indicated by o is shared by three interstitials I_0, I_1 and I_2 . The atomic indices are assigned based on the distance from the origin and the symmetry to aid visualization. The experimental D_{2d} symmetry of the di-interstitial at room temperature can be explained by the thermal averaging motion of I_0, I_1 and I_2 alternatively occupying four equivalent sites. As the result of a T_i transition, the center atom I_0 “effectively” moves to the corresponding site as indicated by the arrows. Note that black atoms lie below the grey atoms along z axis.

FIG. 3. Schematic potential surfaces along the highly symmetric path of $C_{1h} - C_{2v} - C_{1h}$ transitions for the neutral state (solid line) and for the positively charged state (dashed lines) at a given chemical potential μ . The neutral C_{2v} di-interstitial is metastable and the energy barrier Δ is 0.5 eV. In contrast, the positively charged C_{2v} di-interstitial is stable and the energy difference δ between C_{1h} and C_{2v} di-interstitials is only 0.14 eV.


FIG. 4. (a) Isosurfaces of gap state amplitudes of the C_{1h} di-interstitial, (b) local density of states (LDOS) on the center atom I_0 (solid line) and the dumbbell atoms I_1 - I_2 (dashed line) of the C_{1h} di-interstitial and (c) those of the C_{2v} di-interstitial. The reference energy of (b) and (c) is E_v , the valence band maximum of bulk silicon in the 120-atom supercell A. The calculated bulk conduction band minimum, E_c , is indicated by an arrow and is about 0.8 eV from E_v . The energy gap of the C_{1h} di-interstitial is about 0.5 eV, while the donor and acceptor levels of the C_{2v} di-interstitial are almost degenerate. LDOS of the gap states is highlighted by the black (gray) areas for the donor (acceptor) level.

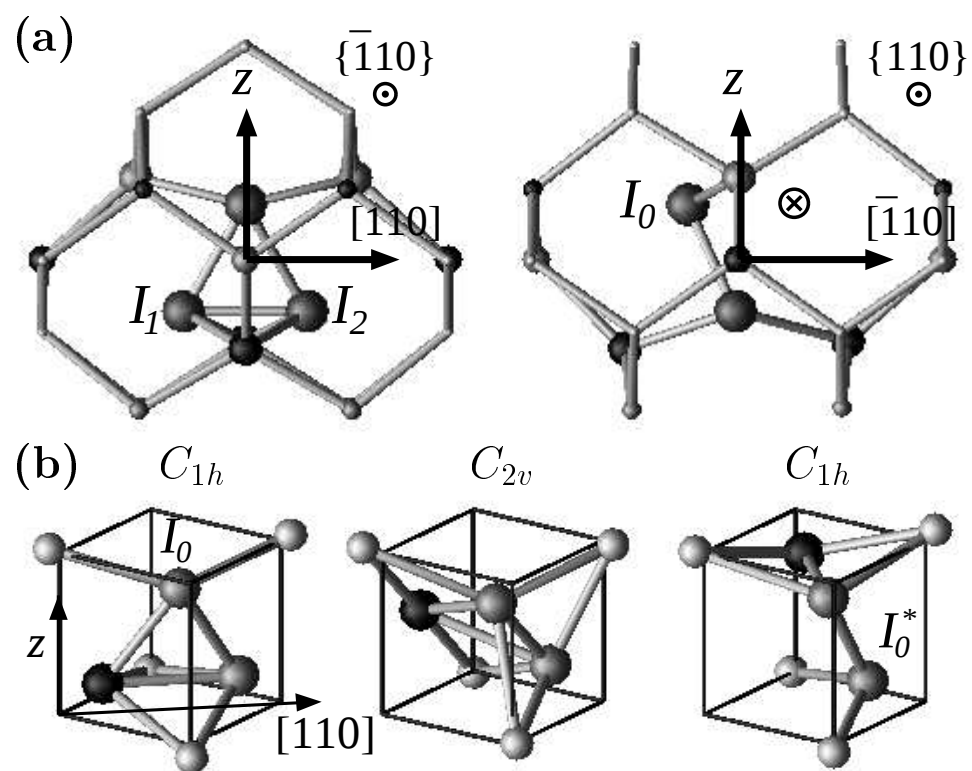


Kim *et al.*, Fig. 1

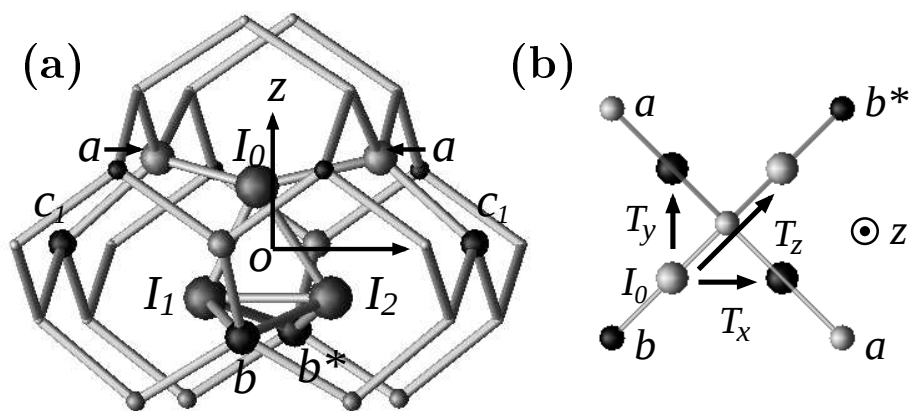

Kim *et al.*, Fig. 2

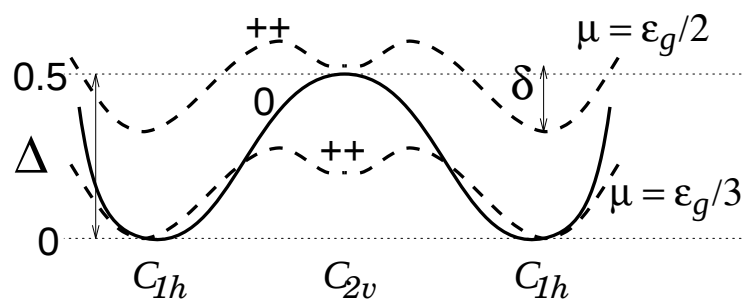

Kim *et al.*, Fig. 3

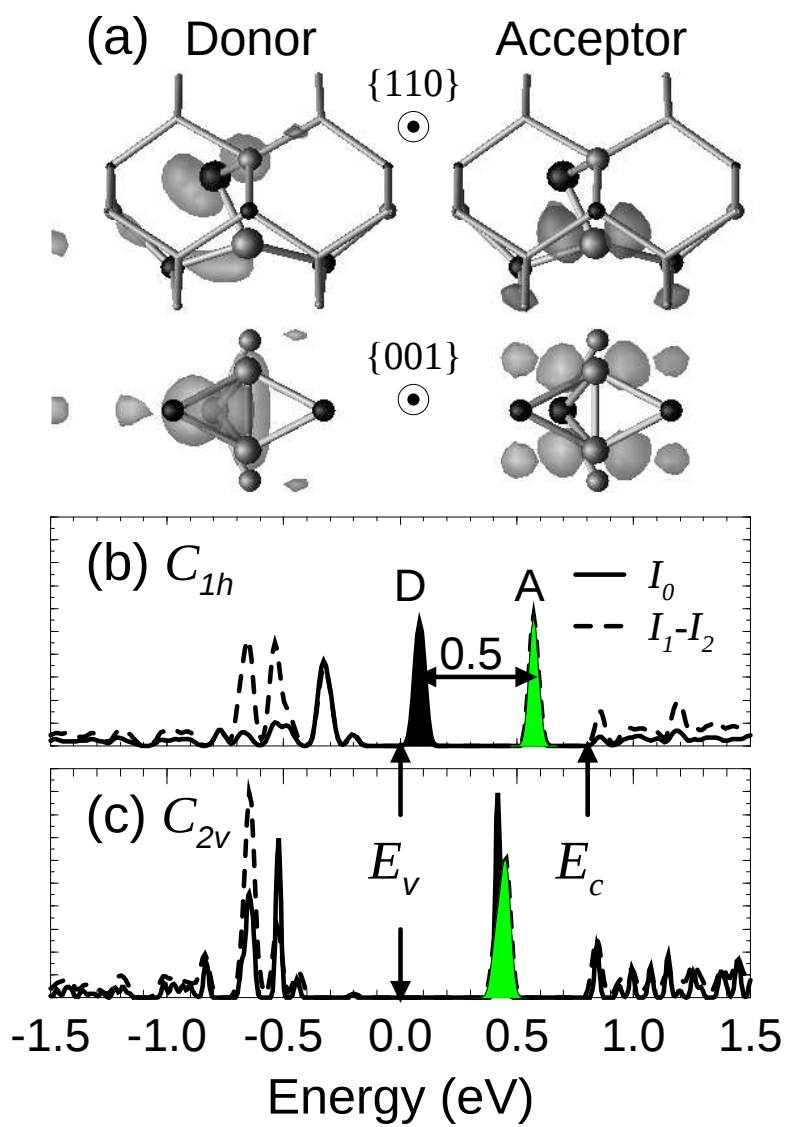

Kim *et al.*, Fig. 4